



Hydrothermal synthesis of surface-modified copper oxide-doped zinc oxide nanoparticles for degradation of acid black 1: Modeling and optimization by response surface methodology

Kamal Salehi¹, Hiva Daraei¹, Pari Teymouri¹, Afshin Maleki¹

¹ Kurdistan Environmental Health Research Center, Kurdistan University of Medical Sciences, Sanandaj, Iran

Original Article

Abstract

Dyes are widely used in various industries most of them are not readily biodegradable and are consisted of number of toxic, mutagenic, and carcinogenic compounds. Therefore, it is essential to remove them from effluent before their discharge to the environment. The objective of this investigation was to synthesize copper oxide (CuO) doped zinc oxide (ZnO) nanoparticles under mild hydrothermal conditions using CuO as dopant and triethylamine as surface modifier to remove acid black 1 from aqueous solutions. Synthesized nanoparticles were characterized using powder X-ray diffractometer, Fourier transform infrared spectroscopy, scanning electron microscopy, and ultra violet-visible spectroscopy. The central composite design matrix and response surface methodology (RSM) were applied for designing the experiment, evaluating the effect of variable and modeling the degradation of acid black 1 dye. The results obtained from analyses of variance indicated that our experiments were fit with quadratic model. Moreover, the optimization R^2 and R^2 adjusted correlation coefficients for model were evaluated as 0.94 and 0.89, respectively. The optimal conditions for high efficiency (100% dye removal) was found to be at catalyst dosage of 1g/l, dye concentration of 50 mg/l, and pH = 6. This investigation introduced the RSM as an appropriate method to model and optimizes the best operating condition for maximizing dye removal. In conclusion, the results showed that nanoparticles dosage plays crucial role in this regard.

KEYWORDS: Hydrothermal, Photocatalysis, Modeling, Response Surface Methodology, Dye Removal, Acid Black 1

Date of submission: 16 Oct 2013, Date of acceptance: 4 Jan 2014

Citation: Salehi K, Daraei H, Teymouri P, Maleki A. **Hydrothermal synthesis of surface-modified copper oxide-doped zinc oxide nanoparticles for degradation of acid black 1: Modeling and optimization by response surface methodology.** J Adv Environ Health Res 2014; 2(2): 101-9.

Introduction

Dyes are macromolecules with high color yield, widely used in various industries such as textile, food, cosmetic, plastic and leather.^{1,2} The average annual production rate of synthetic dyes by industries is about 7 million tons world-wide,³ which about 40% of them are acid dyes. Most acid dyes contain one or more azo (-N = N-) group.^{4,5} Since most of these dyes are not readily biodegradable and are consisted of number of

toxic, mutagenic, and carcinogenic compounds; it is essential to remove them from effluent before their discharge to the environment.⁴⁻⁷

There are several conventional treatment methods for the removal of dyes from effluent stream including flocculation/coagulation, adsorption by activated carbon, electroflocculation, etc.⁸ Nevertheless, these methods are expensive and non-destructive, because they just transfer contamination from liquid to the solid phase.^{9,10} Advanced oxidation processes (AOPs) for removal of organic contamination from wastewater have attracted

Corresponding Author:

Afshin Maleki

Email: maleki43@yahoo.com

considerable attention of many researchers. AOPs are also used for oxidation, removal, and mineralization of dyes and other organic materials in wastewater and effluent.¹¹ They generally involve various methods, including UV/H₂O₂, O₃, O₃/H₂O₂, O₃/UV, O₃/H₂O₂/UV, Fenton, photo and electro-Fenton, and photodegradation.¹²⁻¹⁴

The latter, photo degradation or semiconductor-mediated photo catalyst has been given of great attention over recent years due to its potential to destruct organic contaminants at ambient temperature and pressure.¹⁵ Until now, various semiconductors have been studied by researchers as photocatalyst.^{16,17} Among these semiconductors, TiO₂ is the most widely used because it is non-toxic, inexpensive and photochemically stable.¹⁸ However, zinc oxide (ZnO) is another semiconductor considered as not only a suitable alternative for TiO₂ but also even more efficient than TiO₂ in several applications.¹⁹ The greatest advantage of ZnO in compared with TiO₂ is that it adsorbs a larger fraction of the solar spectrum.²⁰ There are a variety of strategies to tailor the morphology of ZnO nanoparticles, controlling its growth direction, reducing its agglomeration, and enhancing its photo catalytic properties. Doping with suitable materials and using of surface modifiers or capping agents are among the excellent and confirmed techniques used.²¹⁻²³

Therefore, we synthesized copper oxide (CuO) doped ZnO nanoparticles under mild hydrothermal conditions (T = 100 °C, and P = autogenous) using CuO and triethylamine as dopant and surface modifier, respectively. Moreover, we used response surface methodology (RSM) to design experimental and to evaluate the variable effect on photodegradation of acid black 1.

Materials and Methods

Reagent grade ZnO, CuO, triethylamine and KOH were purchased from Merck, Germany. Type I Water and distilled water were produced

by a TKA smart 2 ultrapure water production system (Thermo Electron LED GmbH, Germany). The acid black 1 (Alvan Sabet Co. Iran) was used as a model pollutant from textile industry. Figure 1 shows the chemical structure and some characteristics of this dye figure 1.

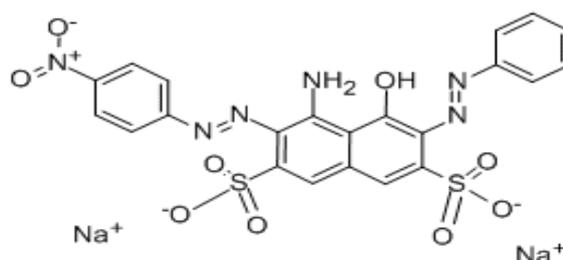


Figure 1. Chemical structure of acid black 1

Surface modified CuO-doped ZnO hybrid nanomaterials were fabricated under mild hydrothermal conditions (T = 100 °C, P = autogenous, t = 8 h). 2 mole of ZnO was taken as starting material and the dopant, CuO, at 0.5, 1, 1.5, 2 and 2.5 weight % was added into it. A certain amount of 1 mole KOH was added as mineralizer to the precursors. At the same time, a fixed concentration (1 ml) of triethylamine was added to the above-mentioned mixture and it was stirred vigorously for a few minutes. The final compound was then transferred to the Teflon liner (V_{fill} = 10 ml), which was later placed inside a general purpose autoclave. Then the assembled autoclave was kept in an oven with a temperature programmer-controller for 8h. The temperature was kept at 100 °C. After the experimental run, the autoclave was quenched to the room temperature. The product in the Teflon liner was then transferred to a clean beaker, washed with double distilled water several times, and then allowed to settle down. The surplus solution was removed using a syringe. Then, the remnant was allowed to dry naturally at room temperature. The dried particles were subjected to systematic characterization and photocatalytic studies.²¹

Fourier transform infrared spectroscopy

(FTIR) spectra of the grade reagent ZnO and the CuO-doped ZnO were obtained by employing a Bruker-Tenso r27 spectrophotometer spectrum, one within wavelength range of 450-4000/cm. Powder X-ray diffraction (XRD) was performed on a Bruker D8-Advance powder XRD by monochromatized Cu KR radiation ($\lambda = 1.5418 \text{ \AA}$). Scanning electron microscopy (SEM) was used to analyze the morphology of the samples.

In this study, five types of synthesized xCuO:ZnO ($x = 0.5, 1.0, 1.5, 2.0$ and 2.5 wt. % of CuO content) were used for dye removal. A total volume of 200 mL of acid black 1 solutions was prepared using double distilled water for investigation of the photo catalyst activity of CuO:ZnO. The CuO-ZnO (0.4, 0.6, 0.8, 1.0, and 1.2 g/l) was mixed with Acid black 1 solutions (50, 100, 150, 200 and 250). The initial pH of the solutions was adjusted before the experiments by 0.1 N NaOH and HCl, and controlled using pH meter (Model WTW-340I). Then, the suspensions were dispersed by vigorous stirring to make a good dispersion of nano-sized ZnO particles. Afterwards, suspension exposed to UV light (30 w) for up to 90 min. All experiments were performed at room temperature ($25 \text{ }^\circ\text{C}$). Dye sample of about 5-8 ml was taken out at the end of experiment using 10 ml pipettes. Each sample was centrifuged (10 min at 5000 rpm) and the absorbance was recorded using a UV-Vis spectrophotometer (Model CECIL 2021) at $\lambda_{\text{max}} = 618 \text{ nm}$. The degradation efficiency (R%) was calculated using the following equation.

$$R(\%) = \frac{A_0 - A}{A_0} \times 100 \quad (1)$$

Where, A_0 and A are the dye concentration (mg/l) at time 0 and t , respectively.

In this investigation, the degradation of acid black 1 in the presence of UV radiation using CuO:ZnO was optimized by RSM using Design Expert Software (Version 7, Stat-ease, Inc., Minneapolis, MN, USA). The runs were designed in accordance with central composite and carried out batch wise. Independent variables for this investigation were catalyst dosage, pH and dye

concentration, which were coded with low and high level in central composite. Table 1 shows the ranges and the level of the investigated variables.

Table 1. Experimental design of photocatalyst degradation of acid black 1 using copper oxide doped zinc oxide

Factor	Name	Low actual	High actual
X ₁	Dye concentration (mg/l)	50	250
X ₂	Nano dose (g/l)	0.4	1.2
X ₃	Ph	4	8

The total numbers of experiments for the three independent variables were determined according to the following equation:

$$N = 2^n + 2n + n_c = 2^3 + 2 \times 3 + 6 = 20 \quad (2)$$

Where, n and n_c are the number of independent variables and center points, respectively.²⁴ The center points are used to estimate the experimental error. The α value in this study was fixed at 2.

After completing the experimental design, the experiments of dye removal were carried out to obtain appropriate model. The experimental data were analyzed by quadratic models. The general form of the quadratic models is shown as follow:

$$Y = \beta_0 + \sum_{j=1}^k \beta_j x_j + \sum_{j=1}^k \beta_{jj} x_j^2 + \sum_{i < j}^k \beta_{ij} x_i x_j + e_i \quad (3)$$

Where, η is response, x_i, x_j are variable, β_0 is the constant coefficient β_j is coefficient of linear, β_{jj} is coefficient of quadratic and β_{ij} is coefficient of interaction and e_i is error.²⁵

Results and Discussion

Morphological characterizations

The SEM image indicates that the synthesized nanoparticles had different size and heterogeneous morphology; among them tetragonal nanoparticles were more obvious. Furthermore, there was no agglomeration on the surface of synthesized nanoparticles (Figure 2). In addition, the change in the morphology could be contributed to the applied surface modifier.²¹

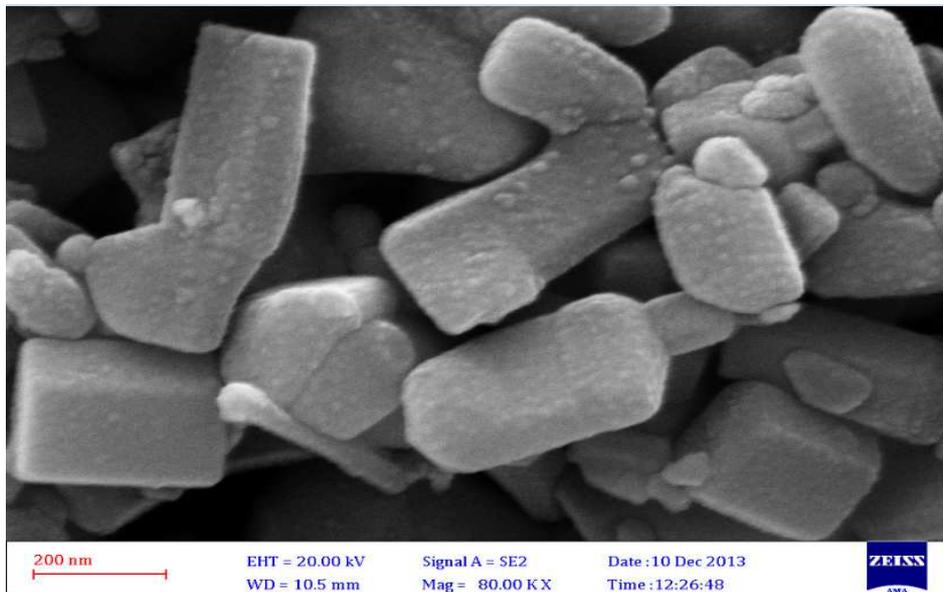


Figure 2. Standard error of the mean image of in situ surface modified zinc oxide doped copper using 1 ml triethylamine

Figure 3 shows the FT-IR spectrum of ZnO (carve A) and 1.50 % CuO-doped ZnO (carve B) nanoparticle recorded in the range of 400-4000/cm. Carve B in figure 3 shows the FT-IR spectrum of CuO-doped ZnO nanoparticle. The broadband at 2800-3000/cm is assigned to the C-H/cm group on the surface modifier. Peaks observed at 1600, 1500, 1400/cm corresponds to N-H, CH₂, CH₃ bonds stretching, respectively. Next peak around 1300/cm is due to the presence of the C-N group. The peak at 750/cm attributes to the Cu-O bond stretching and peak at 500-600/cm indicates stretching vibration of ZnO nanoparticles.

The XRD pattern of fabricated 1.50% CuO/ZnO nanoparticles is shown in figure 4. The diffraction peaks (100, 002 and 101) in figure 4 show that the fabricated nanoparticles are hexagonal structures.²⁶ Average crystallite size were determined using the Debye-Scherrer formula and the value was obtained 54nm for the fabricated nanoparticles. The formula is given below:

$$D_{\text{Scherrer}} = \frac{k\lambda}{\beta \cos\theta} \quad (4)$$

Where, D is the average crystallite size, λ is the radiation wavelength (1.5418Å), k is related to the crystallite shape (k = 0.089), β is the peak width at half maximum, and θ is the Bragg diffraction angle.²⁷ Also increased value of lattice parameter clearly indicates that the CuO ions substitute for Zn in ZnO lattice (Table 2).

Modelling and optimization of acid black 1

The experimental results of dye degradation by synthesized nanoparticles were analyzed through RSM to obtain an empirical model. Quadratic model were used to explain mathematical relationship between independent and depended variables. The mathematical expression of the relationship between acid black 1 degradation and the X₁, X₂, X₃ variables is shown in equation 3.

$$R = 78.1 - 0.072 \times X_1 + 65.36 \times X_2 + 63.75 \times X_3 + 0.2025 \times X_1 \times X_2 - 5.5 \times X_1 \times X_3 + 0.25 \times X_2 \times X_3 - 4.25 \times X_1^2 - 53.43 \times X_2^2 - 0.05 \times X_3^3 \quad (5)$$

In equation (4), R is response decolonization percent, X₁, X₂ and X₃ are corresponding to independent variables of dye concentration (mg/l), catalyst dosage (g/l) and pH, respectively. Analyses of variance results of

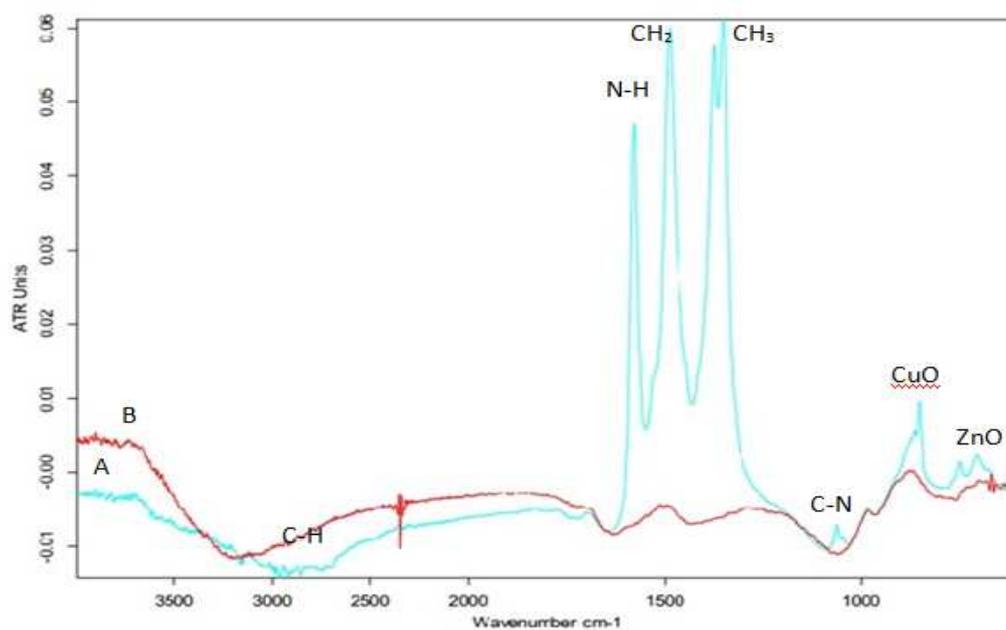


Figure 3. Fourier transform infrared spectrum of in situ surface modified zinc oxide doped copper using 1 ml triethylamine

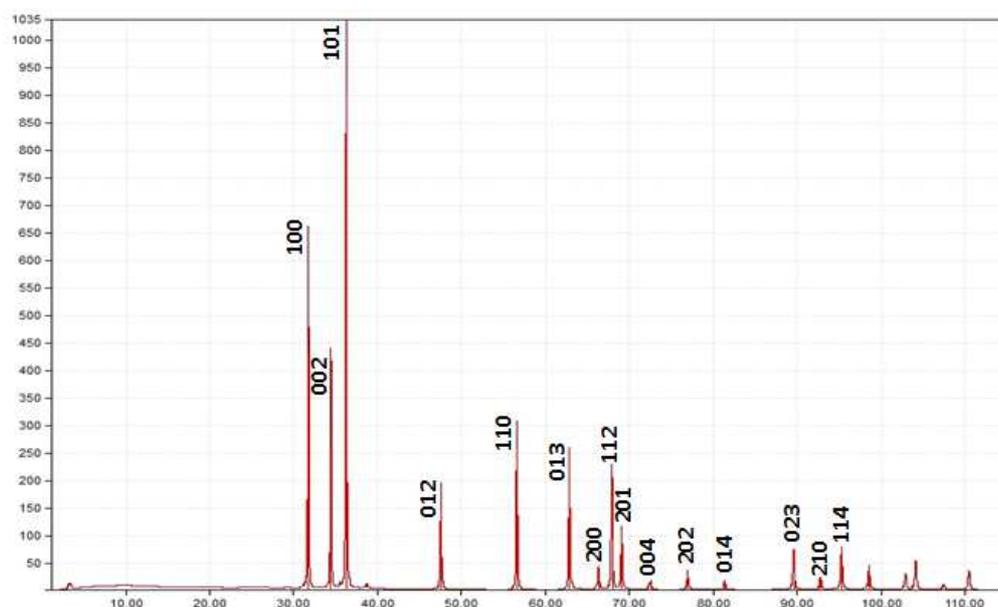


Figure 4. X-ray diffraction pattern of in situ surface modified zinc oxide doped copper using 1 ml triethylamine

Table 2. Lattice parameters of surface modification copper:zinc oxide hybrid nanoparticle

Catalyst	a (Å)	c (Å)	a:c ratio	v (Å)	Reference
Reagent-grade ZnO	3.249	5.207	0.6239	47.60	(8)
CuO:ZnO	3.255	5.214	0.6242	47.86	Present work

CuO: ZnO: Copper oxide: zinc oxide

these quadratic models are presented in table 3. They indicate that these quadratic models can be used to navigate the design space.

As shown in table 3, the quadratic model (F-value = 18.78) implies that the model is significant for degradation of acid black 1. With an adequate precision, the signal to noise ratio can be measured, and a ratio < 4 is generally desirable.²⁸ Therefore, in the quadratic models of degradation Acid black 1, the ratio of 13.79 indicates an adequate signal.

The values of Prob > F < 0.05 and > 0.1000 indicate that the model terms are significant and not significant, respectively. In this study, the

Prob >F values are significant for X_1 , X_2 , but not significant for X_3 , X_1^2 , X_2X_3 , X_1X_2 (Table 3). The “lack of fit F-value” of 4.51 shows that the lack of fit is not significant and the model is adequate.

The actual and predicted acid black 1 dye degradation are shown in figure 5. Actual values and predicted values were measured from response data for a particular run and the model, respectively. The results showed that the predicted values obtained are approximately close to the actual value (Figure 5). Moreover, it was found that the developed models were effectual in taking correlation between nanoparticles type variables and degradation of dye.

Table 3. ANOVA result of the quadratic model of photocatalyst degradation of acid black 1 using copper oxide doped zinc oxide

Source	Sum of Square	DF	Mean Square	F	P
Model	462.08	9	51.34	18.78	< 0.0001
X_1	203.0	1	203.6	74.29	< 0.0001
X_2	88.36	1	88.36	32.32	< 0.0001
X_3	5.52	1	5.52	2.02	0.1230
X_1X_2	32.81	1	32.81	12	0.1856
X_1X_3	0.60	1	0.60	0.22	0.0061
X_2X_3	0.02	1	0.020	7.31	0.6481
X_1^2	28.38	1	28.38	10.38	0.9335
X_2^2	114.88	1	114.88	42.03	0.0091
X_3^2	0.063	1	0.063	0.023	< 0.0001
Residual	27.33	10	2.73	-	0.8825
lack of fit	22.37	5	4.47	4.51	0.0619

DF: Degree of Freedom; X_1 : Dye concentration, X_2 : Nanoparticle dose, X_3 : pH

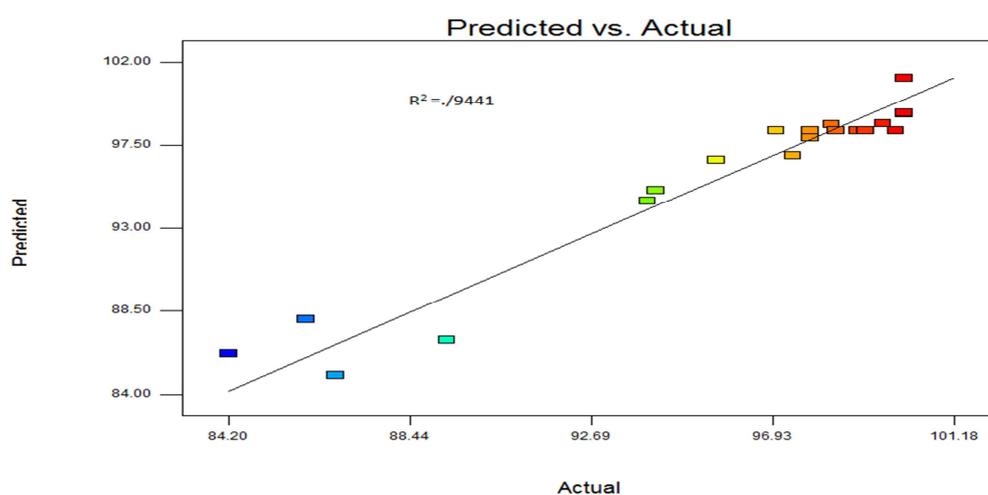


Figure 5. The actual and predicted plot of degradation of acid black 1 ($R^2 = 0.9441$ and $R_{adj} = 0.8949$)

The correlation coefficient (R^2) value is usually in range 0-1. The model is stronger and can better predict the responses when R^2 values are closer to 1.²⁹ The results in this study indicated that the values of R^2 and adjusted R^2 (R^2_{adj}) were found to be 0.94 and 0.89, respectively. X_3 terms in table 1 are not significant, which can be the reason for R^2_{adj} of 0.89.

The effects of variables on acid black 1 degradation are shown in figures 6 and 7 figure 6 shows the 3D response surface plot of interaction between varying concentration of dye and nanoparticles on dye degradation efficiency at pH = 6. The surface plot shows the decrease in dye degradation with increase in dye concentration. Although, degradation increased with catalyst dosage up to 1 g/l catalyst, and then decreased with its increase. The surface plot also shows that the best degradation (100%) obtained at 50 mg/l dye, pH = 6 and 1 g/l nanoparticle dosage.

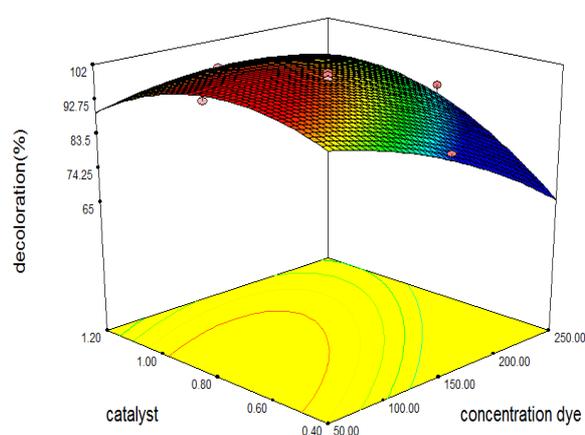


Figure 6. The effect of initial acid black 1 concentration (in mg/l) and nanoparticles (copper oxide doped zinc oxide) dose (in g/l) on decoloration of acid black 1 (pH = 6)

Bragti and Rauf reported that the decrease in degradation might be attributed to the increasing levels of catalyst causing the solution to become turbid and intercept the penetration of light.³⁰ A

study by Marugesan et al. showed that by increasing the concentration of dye from 25 to 100 mg/l, the degradation rate for reactive black removal decreased.³¹ Furthermore, Tekin and Saygi reported that by increasing the dye level from 25 to 35 mg/l, the degradation rate for acid black 1 removal decreased.³² The degradation efficiency can prohibit light penetration, or reduce activated sites for adsorption of hydroxyl ion and generation of hydroxyl radicals. Because with increase in dye concentration, more dye substances are adsorbed on the nanoparticles' surface, and then, prevents generation of hydroxyl radicals.³³ Figure 7 illustrates the effect of changing dye concentration, nanoparticles dosage and pH on photodegradation efficiency of acid black 1. As figure 7 indicates, the dye degradation efficiency is proportion with photo catalyst dosage. Maximum degradation ($\eta > 98\%$) of acid black 1 was determined at constant dye concentration of 150 mg/l, nanoparticles dosage of 1 g/l and pH = 6.

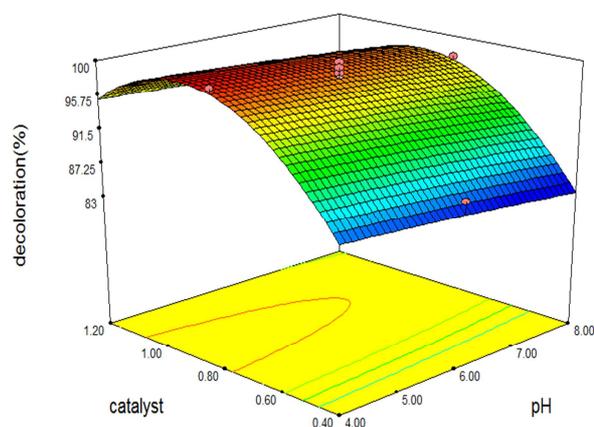


Figure 7. The effect of initial nanoparticles dose (copper oxide doped zinc oxide) and pH on degradation of acid black 1

Conclusion

We synthesized CuO: ZnO nanoparticle under mild hydrothermal condition (P = autogenous, T = 100 °C, t = 8h). The synthesized nanoparticle

was characterized using powder XRD, FTIR, UV-VIS spectroscopy and SEM. The characterization results revealed that the CuO has been completely doped in ZnO lattice. Using triethylamine surface modifier, no agglomeration was observed. Moreover, the nanoparticles were well dispersed in the medium. FTIR results showed the appearance of new peaks after using the surface modifier. The nanoparticles were used for photodegradation of acid black 1. We carried out the systematic analysis using experimental design by RSM. This study clearly showed that RSM is a suitable method for modeling, and also optimizing the best operating conditions for maximum dye removal. In addition, we found that nanoparticle's dosage plays a crucial role in this regard.

Conflict of Interests

Authors have no conflict of interests.

Acknowledgements

The present study is a part of the master thesis of Mr. K. Salehi. The authors would like to thank the Vice-chancellor for Research and Technology, Kurdistan University of Medical Sciences for providing the grant of this research study.

References

1. Srivastava R, Rupainwar D. A comparative evaluation for adsorption of dye on Neem bark and Mango bark powder. *Indian J Chem Technol* 2011; 18(1): 67-75.
2. Mahmoodi NM, Hayati B, Arami M, Lan C. Adsorption of textile dyes on Pine Cone from colored wastewater: Kinetic, equilibrium and thermodynamic studies. *Desalination* 2011; 268(1-3): 117-25.
3. Bharathi KS, Ramesh ST. Removal of dyes using agricultural waste as low-cost adsorbents: a review. *Appl Water Sci* 2013; 3(4): 773-90.
4. Elmorsi TM, Riyad YM, Mohamed ZH, Abd El Bary HM. Decolorization of Mordant red 73 azo dye in water using H₂O₂/UV and photo-Fenton treatment. *J Hazard Mater* 2010; 174(1-3): 352-8.
5. Zee F. Anaerobic azo dye reduction [PhD Thesis]. Wageningen, Netherlands: Wageningen University; 2002.
6. Mahajan P, Kaushal J. Degradation of Congo Red Dye in Aqueous Solution by Using Phytoremediation Potential of Chara Vulgaris. *Chitkara Chemistry Review* Volume 1 2013; 1(1): 67-75.
7. Kousha M, Daneshvar E, Dopeikar H, Taghavi D, Bhatnagar A. Box Behnken design optimization of Acid Black 1 dye biosorption by different brown macroalgae. *Chemical Engineering Journal* 2012; 179(0): 158-68.
8. Giwa A, Nkeonye PO, Bello KA, Kolawole EG, Oliveira Campos AM. Solar Photocatalytic Degradation of Reactive Yellow 81 and Reactive Violet 1 in Aqueous Solution Containing Semiconductor Oxides. *International Journal of Applied Science and Technology* 2012; 2(4): 90-105.
9. Chong MN, Jin B, Chow CWK, Saint C. Recent developments in photocatalytic water treatment technology: A review. *Water Research* 2010; 44(10): 2997-3027.
10. Chakrabarti S, Dutta BK. Photocatalytic degradation of model textile dyes in wastewater using ZnO as semiconductor catalyst. *J Hazard Mater* 2004; 112(3): 269-78.
11. Chang SH, Chuang SH, Li HC, Liang HH, Huang LC. Comparative study on the degradation of I.C. Remazol Brilliant Blue R and I.C. Acid Black 1 by Fenton oxidation and Fe⁰/air process and toxicity evaluation. *J Hazard Mater* 2009; 166(2-3): 1279-88.
12. Neamtu M, Yediler A, Siminiceanu I, Kettrup A. Oxidation of commercial reactive azo dye aqueous solutions by the photo-Fenton and Fenton-like processes. *Journal of Photochemistry and Photobiology A: Chemistry* 2003; 161(1): 87-93.
13. Chung, Kim JO. Application of advanced oxidation processes to remove refractory compounds from dye wastewater. *Desalination and Water Treatment* 2011; 25(1-3): 233-40.
14. Palit S. Membrane Separation Processes and Advanced Oxidation Processes of Dyes in Bubble Column Reactor-A Keen and Far Reaching Overview. *International Journal of ChemTech Research* 2012; 4(3): 862-6.
15. Wu YL, Tok AIY, Boey FYC, Zeng XT, Zhang XH. Surface modification of ZnO nanocrystals. *Applied Surface Science* 2007; 253(12): 5473-9.
16. Maleki A, Shahmoradi B. Solar degradation of Direct Blue 71 using surface modified iron doped ZnO hybrid nanomaterials. *Water Sci Technol* 2012; 65(11): 1923-8.
17. Shahmoradi B, Negahdary M, Maleki A. Hydrothermal Synthesis of Surface-Modified, Manganese-Doped TiO₂ Nanoparticles for Photodegradation of Methylene Blue. *Environmental Engineering Science* 2012; 29(11): 1032-7.
18. Ullah R, Dutta J. Photocatalytic degradation of organic dyes with manganese-doped ZnO nanoparticles. *J Hazard Mater* 2008; 156(1-3): 194-200.

19. Qiu R, Zhang D, Mo Y, Song L, Brewer E, Huang X, et al. Photocatalytic activity of polymer-modified ZnO under visible light irradiation. *J Hazard Mater* 2008; 156(1-3): 80-5.
20. Subash B, Krishnakumar B, Pandiyan V, Swaminathan M, Shanthi M. An efficient nanostructured Ag₂S-ZnO for degradation of Acid Black 1 dye under day light illumination. *Separation and Purification Technology* 2012; 96(0): 204-13.
21. Shahmoradi B, Namratha K, Byrappa K, Soga K, Ananda S, Somashekar R. Enhancement of the photocatalytic activity of modified ZnO nanoparticles with manganese additive. *Research on Chemical Intermediates* 2011; 37(2-5): 329-40.
22. Chen J, Yao M, Wang X. Investigation of transition metal ion doping behaviors on TiO₂ nanoparticles. *J Nanopart Res* 2008; 10(1): 163-71.
23. Ueda K, Tabata H, Kawai T. Magnetic and electric properties of transition-metal-doped ZnO films. *Appl Phys Lett* 2001; 79: 988.
24. Sahu JN, Acharya J, Meikap BC. Response surface modeling and optimization of chromium(VI) removal from aqueous solution using Tamarind wood activated carbon in batch process. *J Hazard Mater* 2009; 172(2-3): 818-25.
25. Zheng Y, Wu XM, Branford-White C, Quan J, Zhu LM. Dual response surface-optimized process for feruloylated diacylglycerols by selective lipase-catalyzed transesterification in solvent free system. *Bioresour Technol* 2009; 100(12): 2896-901.
26. Chen YW, Liu YC, Lu SX, Xu CS, Shao CL. Photoelectric properties of ZnO: In nanorods/SiO₂/Si heterostructure assembled in aqueous solution. *Appl Phys B* 2006; 84(3): 507-10.
27. Narayana RL, Matheswaran M, Aziz AA, Saravanan P. Photocatalytic decolourization of basic green dye by pure and Fe, Co doped TiO₂ under daylight illumination. *Desalination* 2011; 269(1-3): 249-53.
28. Ahmadi M, Vahabzadeh F, Bonakdarpour B, Mofarrah E, Mehranian M. Application of the central composite design and response surface methodology to the advanced treatment of olive oil processing wastewater using Fenton's peroxidation. *J Hazard Mater* 2005; 123(1-3): 187-95.
29. Kaushik R, Saran S, Isar J, Saxena RK. Statistical optimization of medium components and growth conditions by response surface methodology to enhance lipase production by *Aspergillus carneus*. *Journal of Molecular Catalysis B: Enzymatic* 2006; 40(3-4): 121-6.
30. Korbahti BK, Rauf MA. Response surface methodology (RSM) analysis of photoinduced decoloration of toluidine blue. *Chemical Engineering Journal* 2008; 136(1): 25-30.
31. Murugesan K, Dhamija A, Nam IH, Kim YM, Chang YS. Decolourization of reactive black 5 by laccase: Optimization by response surface methodology. *Dyes and Pigments* 2007; 75(1): 176-84.
32. Tekin D, Saygi B. Photoelectrocatalytic decomposition of Acid Black 1 dye using TiO₂ nanotubes. *Journal of Environmental Chemical Engineering* 2013; 1(4): 1057-61.
33. Giahi M, Badalpoor N, Habibi S, Taghavi H. Synthesis of CuO/ZnO Nanoparticles and Their Application for Photocatalytic Degradation of Lidocaine HCl by the Trial-and-error and Taguchi Methods. *Bulletin- Korean Chemical Society* 2013; 34(7): 2176-82.